

## MasterTop 330

Heavy duty high strength iron aggregate topping

#### **Material Description**

MasterTop 330 is an iron aggregate topping designed to provide industrial floors with extra heavy-duty protection against abrasion and impact. Applied over prepared hardened concrete it gives significantly longer service life than either normal high strength concrete or natural aggregate toppings. MasterTop 330 has a lower modulus of elasticity than other toppings of equivalent compressive strength which increases impact resistance and total energy absorbing capacity (toughness).

#### **Areas of Application**

- Areas subject to heavy abrasive traffic, impact and continuous wear, such as loading docks, aisles, waste transfer facilities, truck or tractor repair areas, and mill scale sluiceways
- Areas where safety authorities have deemed other floor surfaces hazardous because of excessive wear such as dangerously buckled steel plates, etc
- Mining workshops with tracked vehicles
- Floors with scraper blades in constant contact

MasterTop 330 is not recommended for areas where steel plate has worn through in less than one year, or where the floor surface is exposed to chemicals that would affect a concrete floor. For applications under these service conditions Ucrete may be a better option

#### **Characteristics & Benefits**

- Ease of application extended working life at screedable consistency (130 to 180mm slump) allows ample time to place, float and finish. Rotary compactors are not required.
- Heavy duty, durable industrial floor topping formulated to be applied at a thickness of 13 to 40mm. Thickness chosen depends on project requirements, including design traffic loading, abrasion, impact and chemical resistance. Refer to the MasterTop 330 Application Guide for more information.
- High abrasion resistance eight times more wear resistance than plain concrete.

- Greater toughness energy absorbing capacity is significantly greater than normal high strength concrete or natural aggregate toppings.
- Increased impact resistance four times greater than plain concrete.
- High density surface resists oil and grease penetration, reduces dusting and absorption.
- Protects against joint deterioration iron armouring eliminates the risk of dangerous protruding or buckled joints from steel tiles, minimises damage to production goods and increases the life of materials handling equipment.

#### **Properties**

#### **Compressive Strength**

Typical compressive strengths for 50mm cubes, cured at  $21^{\circ}$ C, mixed to the recommended consistency using 2.0 litres of water per 20kg bag.

Age	MPa
<b>Age</b> 24 hours	47
3 days	60
7 days	68
28 days	88

Reasonable variations from the results shown here may be experienced as a result of jobsite conditions. Mix an entire bag of MasterTop 330 when preparing cubes for strength tests.

Abrasion Resistance (ASTM	0.20mm at 60 minutes
C779)	(33MPa concrete more
	than 1.4mm at 60 minutes)
Impact resistance (LA	30% weight Loss (33MPa
Rattler)	concrete has 70% loss of
	weight)

See Technical Sheet 22 for explanation of abrasion and impact tests and how they relate to long-term durability of the floor.


#### **Stress-Strain Tests**

Typical stress-strain test data comparing the basic material properties of MasterTop 330 to 28MPa plain concrete, using 76mmx152mm cylinder cured at 21°C.



## MasterTop 330

Heavy duty high strength iron aggregate topping

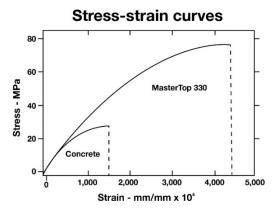

	MasterTop 330	Plain Concrete
Unit weight, kg/m³	3555	2325
Modulus of elasticity, 10 <sup>6</sup> MPa	2.7	3.1
Maximum Strain, mm/mmx 10 <sup>-6</sup>	4450	1620
Toughness, MPa x 10 <sup>-2</sup>	21	3

## **Application**

Please refer to Application Guide for MasterTop 330 for complete application and curing instructions MasterTop 330 is best applied over concrete with a minimum compressive strength of 30MPa.

#### **Estimating Data**

One 20kg bag of **MasterTop 330** mixed with 2.0L potable water provides approximately 6.2L of screedable topping at 150mm slump.

MasterTop 330				
L	Thickness	$m^3$	bags	m²/mm
	in mm /m²		$/m^3$	thickness
6.2	6.2mm	(0.0062)	161	6.2 m <sup>2</sup>

Because the depth of surface preparation may vary from design it is best to overestimate the quantity required by 10-20% for the first stages, until actual usage is established.

### **Packaging**

**MasterTop 330** is packaged in 20kg moisture resistant paper bags.

## **Storage & Shelf Life**

MasterTop 330 can be stored in tightly sealed original bags for 12 months if kept dry and at warehouse temperatures.

#### **Precautions**

For the full health and safety hazard information and how to safely handle and use this product, make sure that you obtain a copy of the Safety Data Sheet (SDS) from our office or website.



# MasterTop 330

Heavy duty high strength iron aggregate topping

### **Disclaimer**

STATEMENT OF RESPONSIBILITY	MasterTop-330 -ANZ-V8-0723  The technical information and application advice given in this MB Solutions Australia Pty Ltd publication are based on the present state of our best scientific and practical knowledge. As the information herein is of a general nature, no assumption can be made as to a product's suitability for a particular use or application and no warranty as to its accuracy, reliability or completeness either expressed or implied is given other than those required by law. The user is responsible for checking the suitability of products for their intended use and for ensuring that the application and use of the product is in accordance with the manufacturer's guidelines and recommendations.		
NOTE	Field service where provided does not constitute supervisory responsibility. Suggestions made by MB Solutions Australia Pty Ltd either orally or in writing may be followed, modified or rejected by the owner, engineer or contractor since they, and not MB Solutions Australia Pty Ltd, are responsible for carrying out procedures appropriate to a specific application.		
MB Solutions Australia ABN 69 634 934 419 II Stanton Road Seven Hills NSW 2147 Freecall: 1300 227 300 www.master-builders-	)	MB Solutions New Zealand Ltd 45C William Pickering Drive Albany, Auckland New Zealand Phone: +64 9 414 7233	Emergency Advice: 1300 954 583 within Australia (24hr) 0800 001 607 within New Zealand